

Fig. 1. Cruciform test configuration and loading arrangement (all dimensions are in mm).

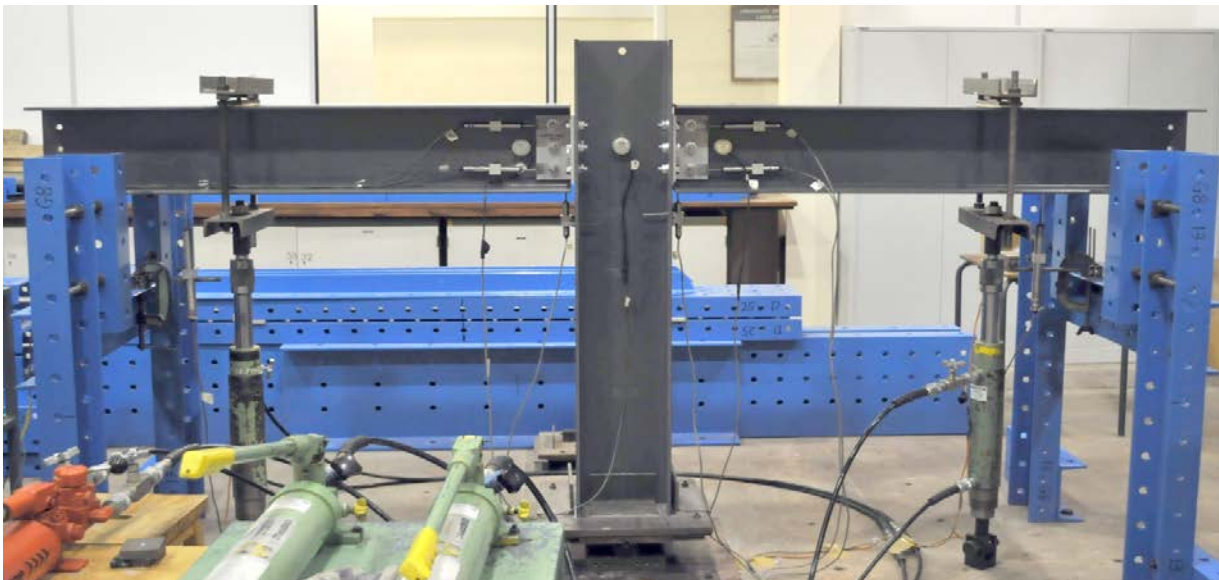


Fig. 2. General test arrangement for major-axis beam-to-column joint Wmj254_3M16_FC1-5.

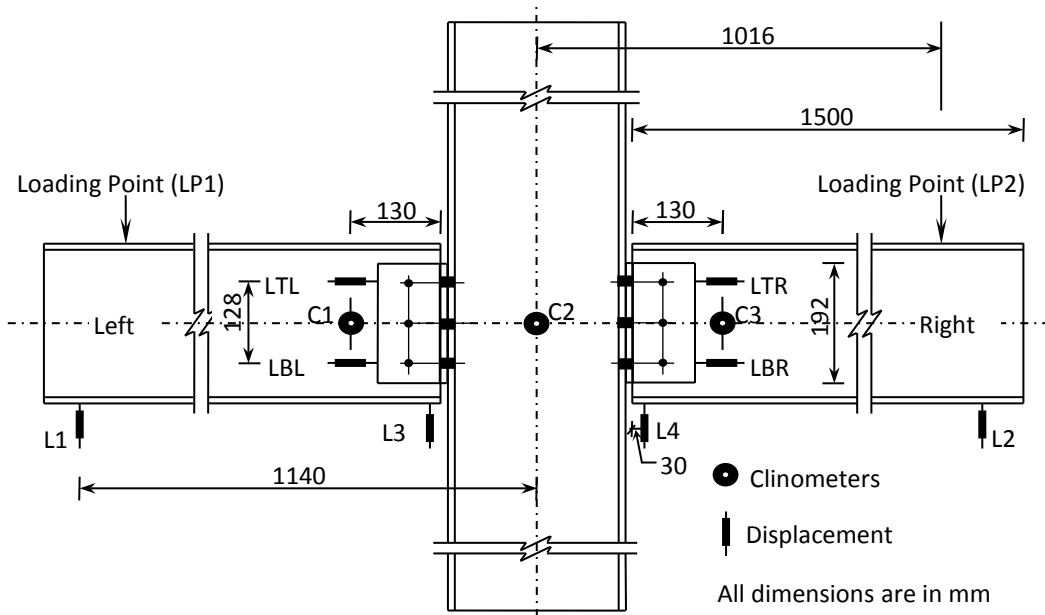


Fig. 3. Location of instrumentation in nominally pinned beam-to-column joint tests (all dimensions are in mm).

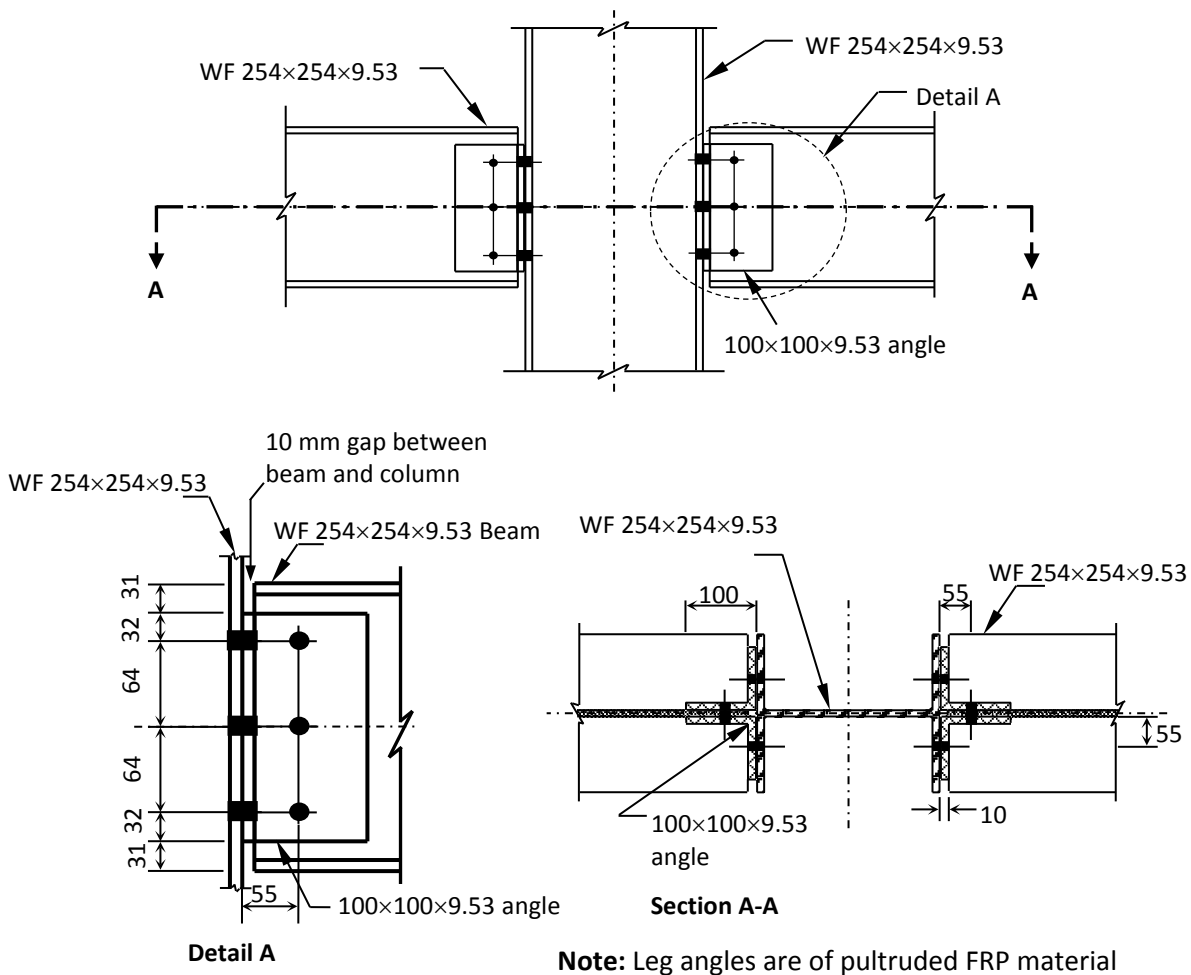


Fig. 4. Connection details for nominally pinned beam-to-column joint tests (all dimensions are in mm), adapted from [Fig. 1].

Test Ref: wmj254_3M16_FC1-5

Test date: 31st October 2011

Moment arm = 1.016 m

Load Incr	LEFT SIDE										Beam deflecti on near column end, L3 (CH13)	Rotation due to horizontal slip, arctan ((LBL-LTL)/L)
	Centre rotation, C2 (CH18)	Load Point, LP1 (CH 21)	Rotation, C1 (CH 17)	Moment =LP1 x moment arm	Joint rotation, (4)-(2)	Slip compensa ted joint rotation, (6)-(12)	End beam deflecti on L1, (CH11)	Slip top, LTL (CH1)	Slip bot, LBL (CH3)			
	mrad	kN	mrad	kN.m	mrad	mrad	mm	mm	mm	mm		
1	2	3	4	5	6	7	8	9	10	11	12	
	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	
	-0.65	0.24	-2.21	0.24	1.56	1.43	2.19	-0.04	-0.03	0.02	0.13	
	-0.72	0.24	-2.49	0.24	1.77	1.55	2.44	-0.06	-0.03	0.02	0.22	
	-0.72	0.24	-2.60	0.24	1.88	1.70	2.55	-0.06	-0.04	0.02	0.18	
	-0.03	0.40	-6.95	0.40	6.92	3.71	6.40	-0.31	0.11	-0.04	3.21	
	0.02	0.40	-7.08	0.40	7.10	3.83	6.50	-0.32	0.10	-0.05	3.27	
	0.03	0.64	-11.22	0.65	11.25	6.48	10.30	-0.42	0.19	-0.04	4.77	
	0.05	0.62	-11.38	0.63	11.42	6.65	10.43	-0.43	0.18	-0.05	4.77	
	0.01	0.86	-15.70	0.87	15.71	9.74	14.40	-0.47	0.29	-0.02	5.97	
	-0.03	0.82	-15.86	0.84	15.83	9.86	14.52	-0.48	0.30	-0.02	6.06	
	0.05	1.04	-19.54	1.05	19.58	13.61	17.89	-0.50	0.34	0.01	6.54	
	-0.02	1.00	-19.66	1.02	19.64	13.67	17.98	-0.50	0.34	0.01	6.59	
	-0.01	0.92	-19.73	0.93	19.72	13.75	18.00	-0.53	0.37	0.02	7.04	
	-0.02	1.25	-24.72	1.27	24.70	18.73	22.71	-0.57	0.39	0.08	7.51	
	-0.04	1.20	-24.84	1.22	24.81	18.84	22.79	-0.57	0.39	0.08	7.52	
	0.83	0.13	-11.78	0.13	12.61	6.64	10.43	-0.56	0.35	-0.12	7.15	
	1.13	0.12	-11.05	0.12	12.18	6.21	9.74	-0.57	0.35	-0.13	7.15	
	1.58	1.28	-24.50	1.30	26.08	20.12	22.34	-0.59	0.39	0.09	7.63	
	1.58	1.23	-24.60	1.25	26.18	20.21	22.42	-0.60	0.38	0.09	7.64	
	-0.10	1.55	-32.98	1.57	32.88	26.91	30.31	-0.62	0.42	0.18	8.07	
	-0.10	1.47	-33.10	1.49	33.00	27.03	30.40	-0.65	0.42	0.19	8.31	
	0.11	1.75	-39.60	1.77	39.71	33.74	36.24	-0.66	0.44	0.29	8.57	
	-0.09	1.62	-39.69	1.65	39.60	33.63	36.29	-0.66	0.45	0.28	8.62	
	-0.48	0.13	-18.02	0.13	17.54	11.57	16.19	-0.63	0.38	-0.06	7.84	
	-0.41	0.11	-16.93	0.11	16.52	10.55	15.18	-0.63	0.36	-0.07	7.78	
	-0.36	1.73	-41.04	1.75	40.69	34.72	37.57	-0.67	0.44	0.30	8.66	
	-0.73	1.63	-41.16	1.65	40.43	34.46	37.67	-0.68	0.44	0.30	8.67	
	-4.35	1.65	-46.95	1.67	42.60	36.63	43.12	-0.69	0.45	0.32	8.87	
	-5.81	1.52	-46.96	1.54	41.15	35.18	43.26	-0.69	0.44	0.29	8.85	
	-6.37	1.46	-46.88	1.48	40.51	34.54	43.25	-0.70	0.44	0.28	8.87	
	-6.56	1.43	-46.84	1.45	40.28	34.31	43.22	-0.70	0.44	0.28	8.86	
	-6.59	1.43	-46.84	1.45	40.25	34.28	43.22	-0.70	0.44	0.28	8.88	
	-6.68	1.41	-46.81	1.43	40.13	34.16	43.21	-0.70	0.43	0.28	8.88	
	0.22	0.13	-19.32	0.13	19.54	13.57	17.33	-0.68	0.37	-0.03	8.13	

	0.19	0.13	-18.69	0.14	18.88	12.91	16.73	-0.67	0.36	-0.04	8.09
	0.19	0.14	-18.51	0.14	18.70	12.73	16.57	-0.67	0.37	-0.04	8.07

Note: L is vertical separation between two horizontal displacement transducers on the web cleat = 128 mm

Green: indicates linear elastic joint properties

Red: shows joint properties at damage onset or when first crack appears in FRP cleats

Blue: indicates joint properties at maximum moment

After damage onset (red values), it is assumed that steel bolt is bearing into FRP material.

Any slip rotation after damage onset is due to bearing and is not subtracted from joint rotation.

	Initial	Moment	Rotation
Left		0.45	4.2
Right		0.45	4.1

Determined from Moment rotation curves

Test Ref: wmj254_3M16_FC1-5

Test date: 31st October 2011


Moment arm =

1.016 m


RIGHT SIDE									
Load Point, LP2 (CH 22)	Rotation C3 (CH 19)	Moment =LP2 x moment arm	Joint rotation, (14)-(2)	Slip compensated joint rotation, (16)-(22)	End beam deflection L2, (CH9)	Slip top, LTR (CH5)	Slip bot, LBR (CH7)	Beam deflection near column end, L4 (CH15)	Rotation due to horizontal slip, arctan ((LBR-LTR)/L)
kN	mrad	kN.m	mrad	mrad	mm	mm	mm	mm	mrad
13	14	15	16	17	18	19	20	21	22
0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00	0.00
0.26	1.91	0.27	2.56	2.52	1.71	-0.03	-0.03	0.03	0.04
0.28	2.11	0.29	2.83	2.74	1.87	-0.04	-0.03	0.03	0.09
0.28	2.17	0.28	2.89	2.84	1.93	-0.05	-0.04	0.03	0.05
0.44	4.26	0.45	4.29	4.14	3.94	-0.06	-0.04	0.05	0.16
0.44	4.39	0.45	4.37	4.21	4.06	-0.07	-0.05	0.05	0.16
0.68	7.03	0.69	7.00	6.60	6.41	-0.09	-0.03	0.08	0.40
0.66	7.14	0.67	7.09	6.67	6.48	-0.09	-0.04	0.08	0.42
0.90	10.53	0.91	10.52	9.69	9.52	-0.12	-0.01	0.11	0.84
0.86	10.59	0.87	10.62	9.78	9.52	-0.13	-0.02	0.11	0.91
1.07	13.56	1.08	13.51	12.67	12.27	-0.18	0.01	0.13	1.44
1.03	13.57	1.05	13.59	12.75	12.28	-0.17	0.01	0.13	1.45
0.95	13.74	0.97	13.75	12.91	12.37	-0.19	0.01	0.13	1.55
1.28	18.81	1.30	18.83	18.00	16.94	-0.27	0.02	0.17	2.20
1.23	18.89	1.25	18.92	18.09	17.00	-0.27	0.02	0.17	2.26
0.17	8.45	0.18	7.62	6.78	7.47	-0.25	-0.01	0.01	1.87
0.16	8.40	0.16	7.27	6.43	7.48	-0.25	-0.01	0.01	1.87
1.31	21.67	1.33	20.09	19.26	19.64	-0.29	0.01	0.19	2.36
1.26	21.66	1.28	20.08	19.25	19.64	-0.29	0.00	0.19	2.32
1.58	25.94	1.60	26.04	25.21	23.43	-0.34	0.04	0.25	3.00
1.50	26.00	1.53	26.10	25.27	23.48	-0.35	0.04	0.25	3.04
1.77	32.99	1.80	32.88	32.04	29.86	-0.37	0.06	0.34	3.33
1.68	33.12	1.70	33.21	32.37	29.95	-0.39	0.06	0.34	3.46
0.17	11.95	0.17	12.43	11.59	10.42	-0.34	0.00	0.04	2.66
0.16	11.16	0.16	11.57	10.74	9.69	-0.33	0.00	0.03	2.59
1.76	34.63	1.79	34.99	34.15	31.28	-0.39	0.05	0.37	3.47
1.66	34.77	1.68	35.50	34.66	31.35	-0.40	0.04	0.38	3.43
1.68	43.89	1.70	48.24	47.40	39.19	-0.42	0.06	0.57	3.79
1.55	44.23	1.58	50.04	49.21	39.40	-0.42	0.06	0.60	3.77
1.49	44.37	1.52	50.74	49.90	39.48	-0.42	0.05	0.61	3.65
1.47	44.43	1.50	50.99	50.15	39.49	-0.42	0.04	0.61	3.63
1.47	44.42	1.49	51.01	50.18	39.50	-0.43	0.04	0.61	3.69
1.45	44.41	1.47	51.09	50.25	39.45	-0.43	0.04	0.61	3.67
0.17	24.41	0.18	24.19	23.36	21.54	-0.39	-0.02	0.23	2.89


0.18	23.35	0.18	23.16	22.33	20.62	-0.39	-0.02	0.21	2.84
0.18	23.08	0.18	22.89	22.05	20.39	-0.38	-0.02	0.21	2.87


wmj254_3M16_FC1.5

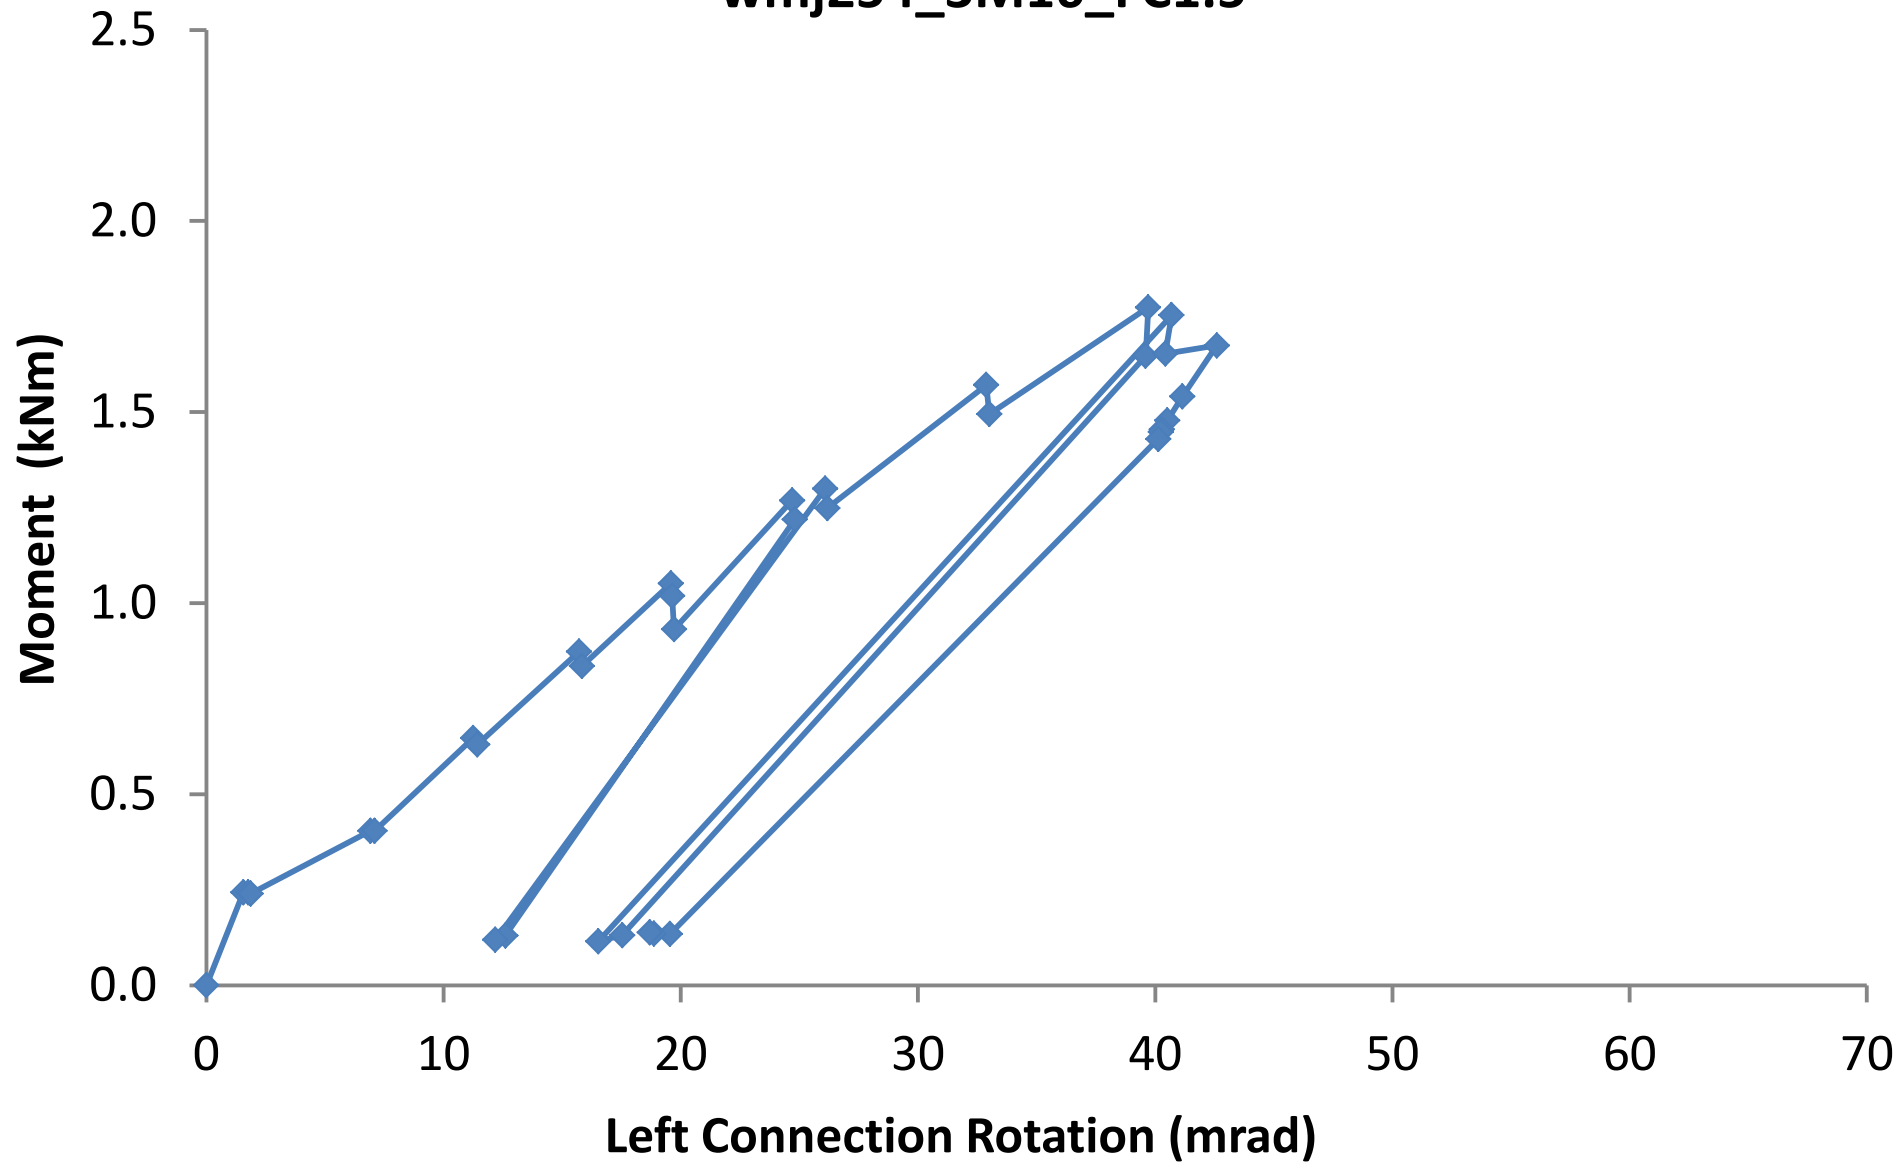


wmj254_3M16_FC1.5

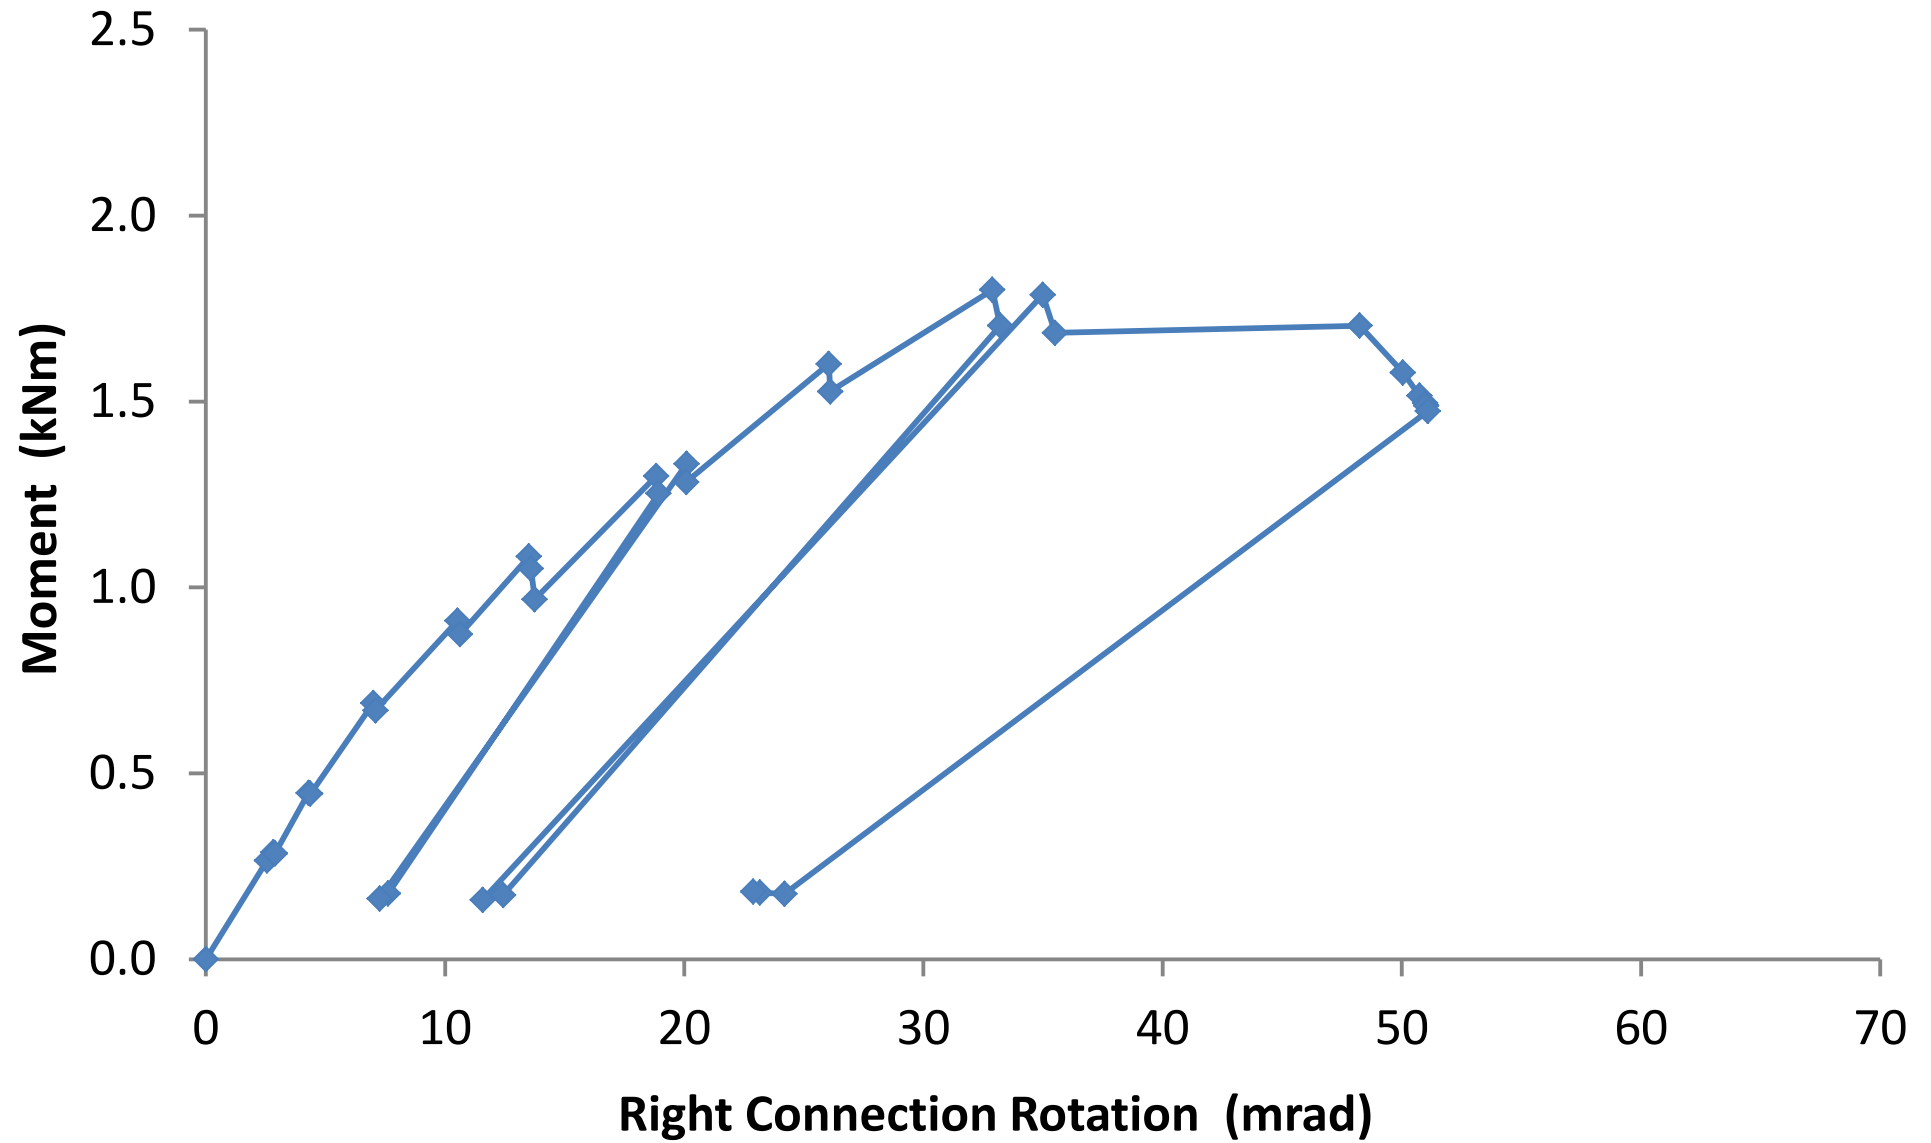

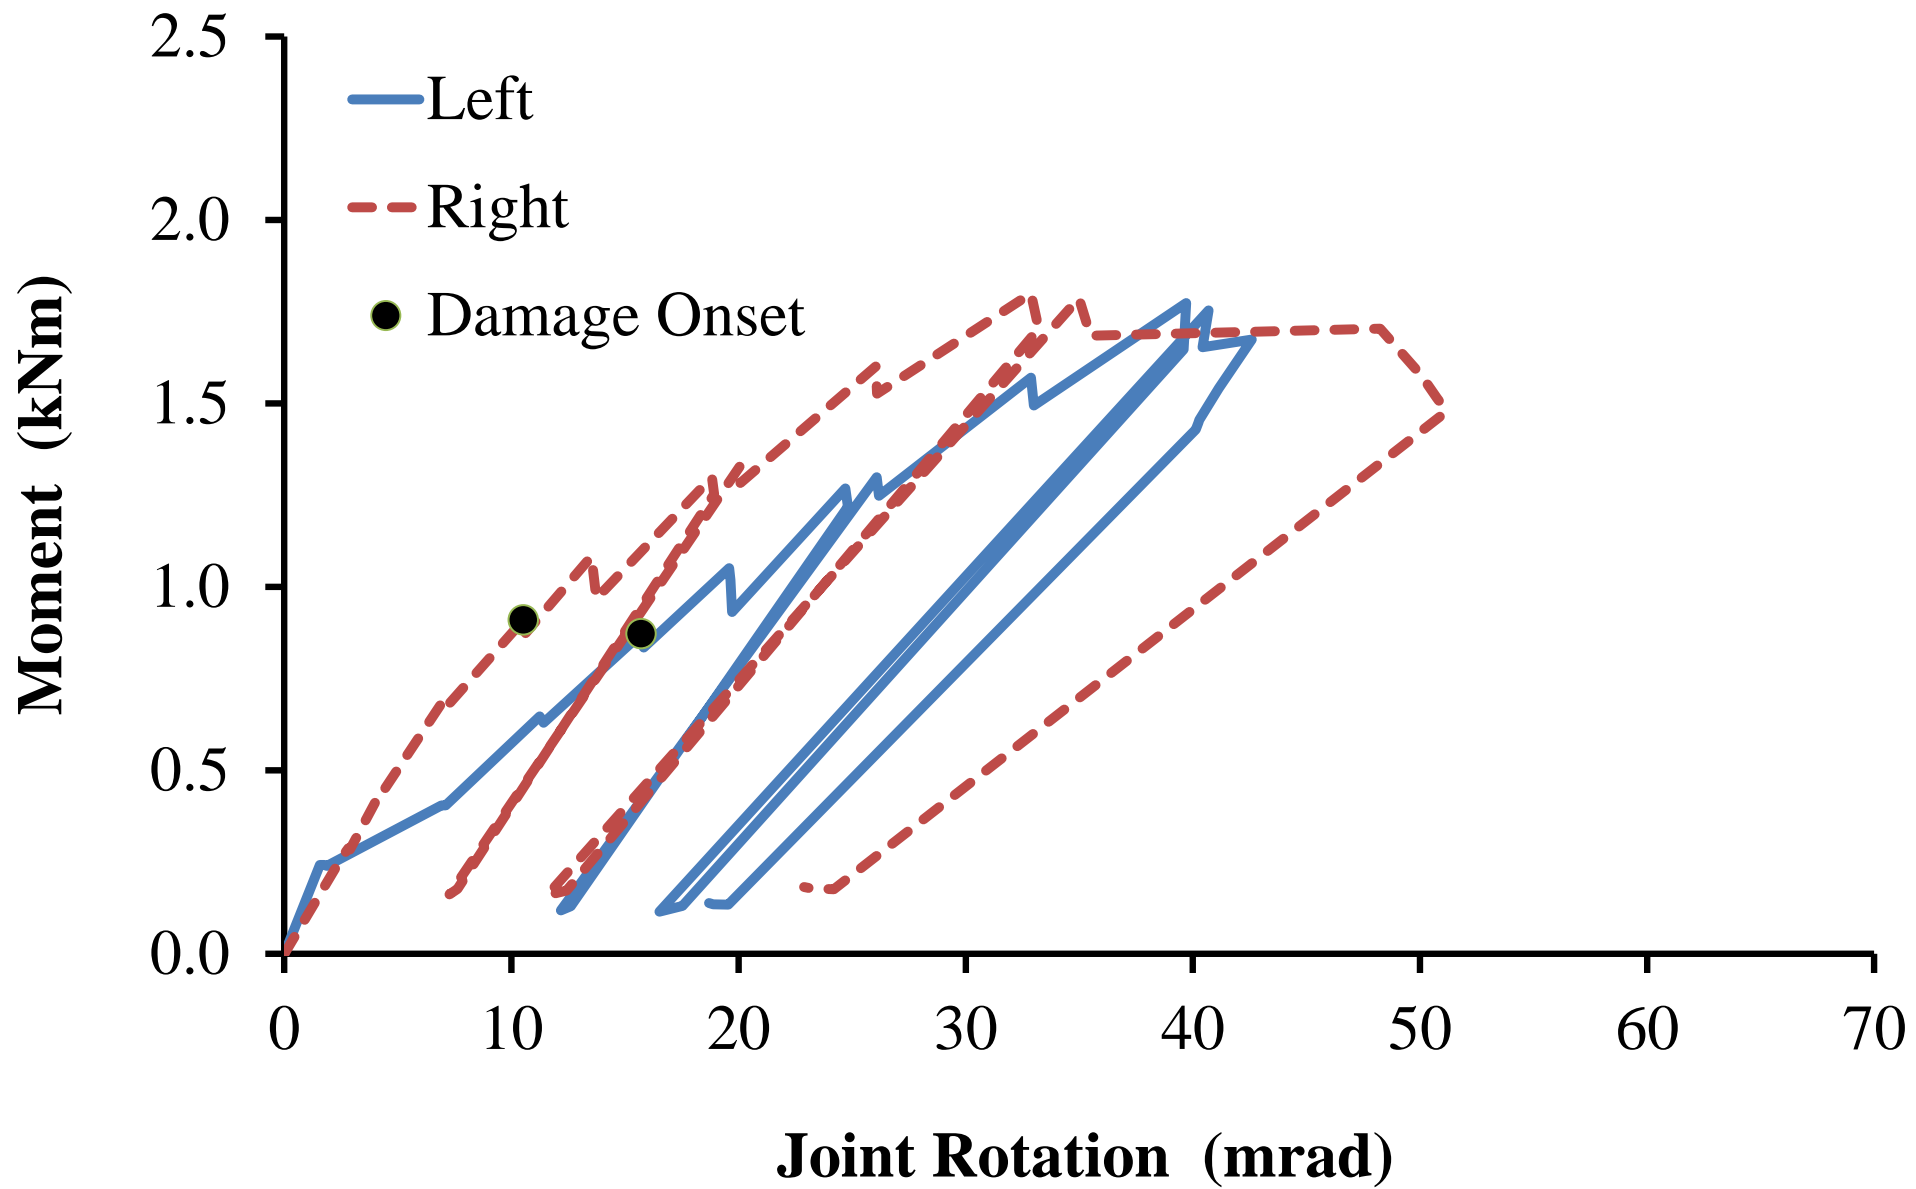

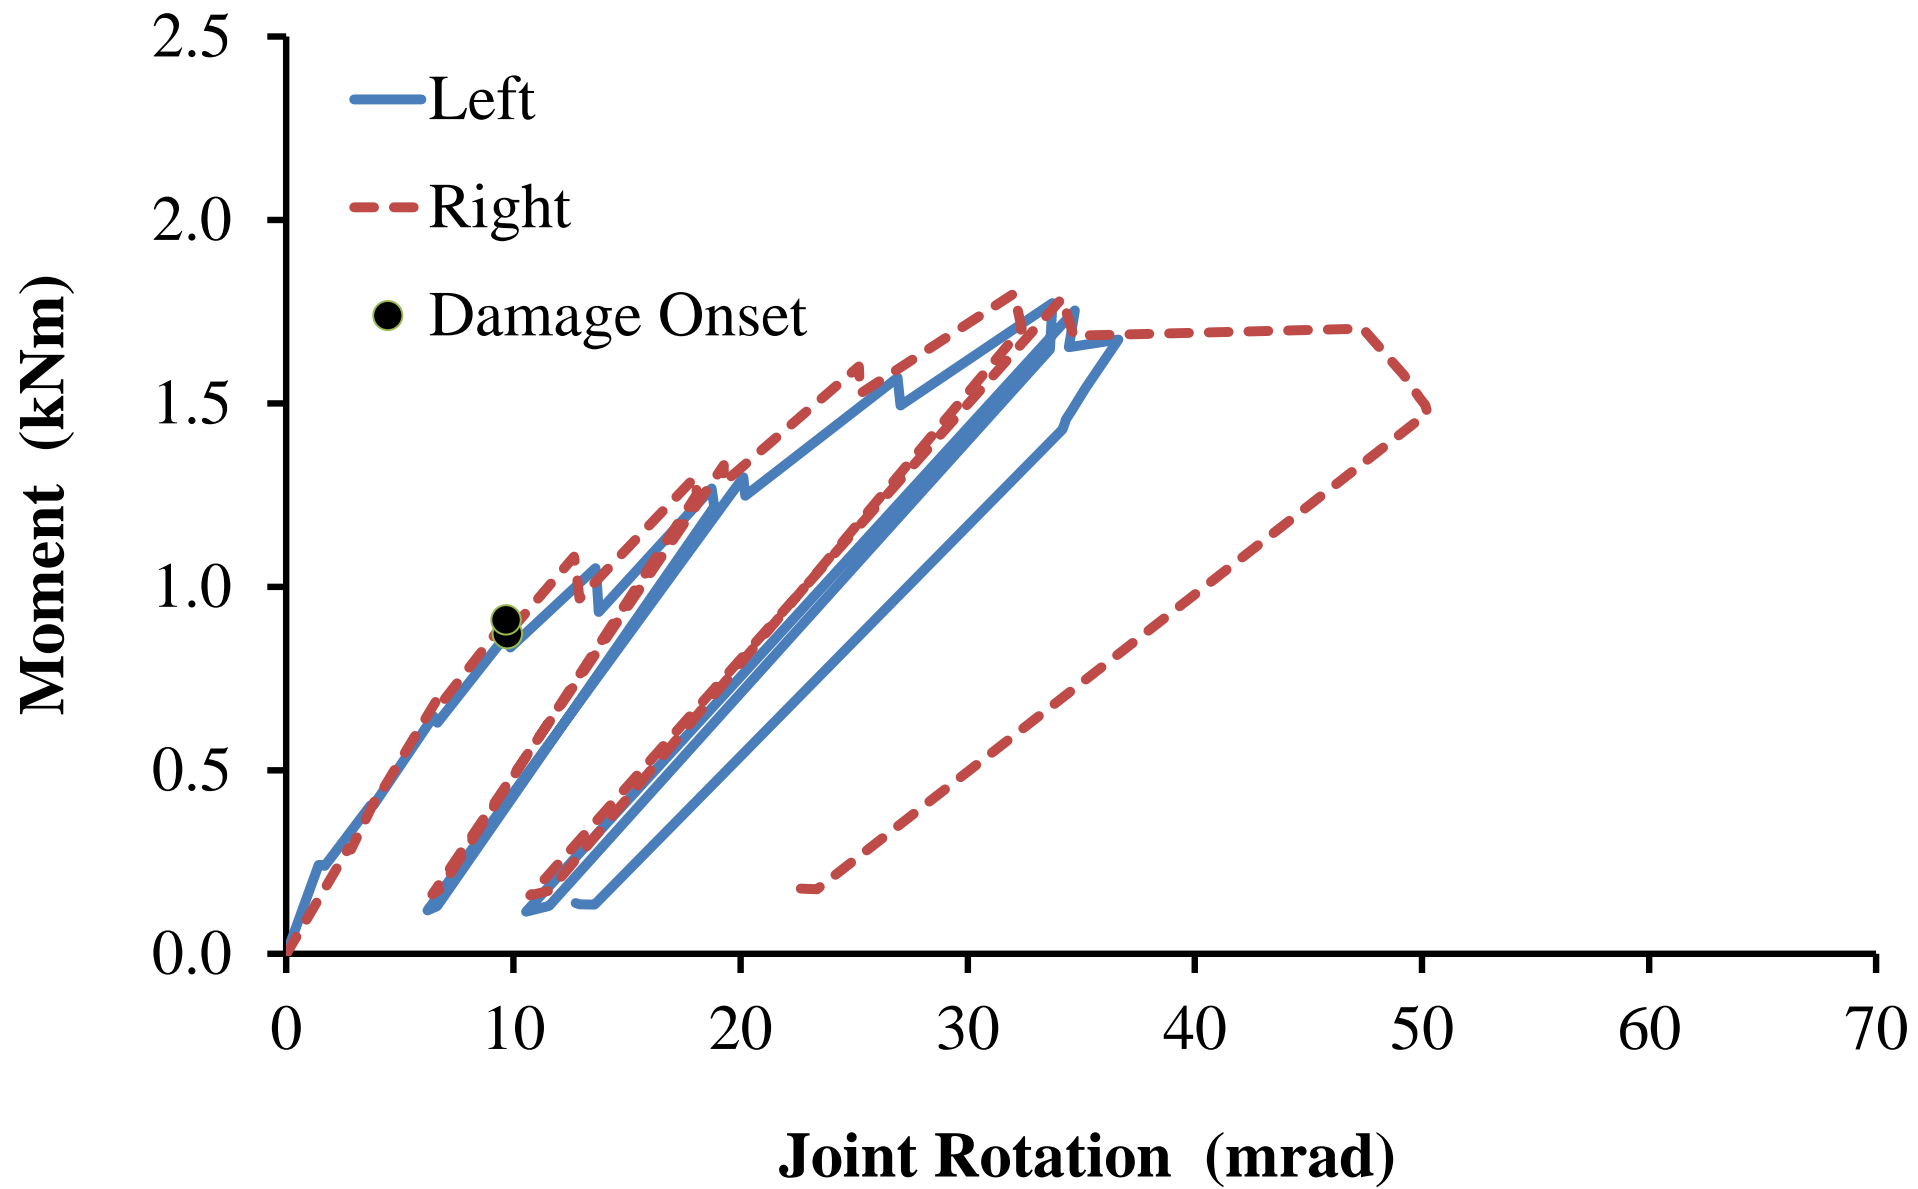

Wmj254_3M16_FC1.5 (Slip Compensated)

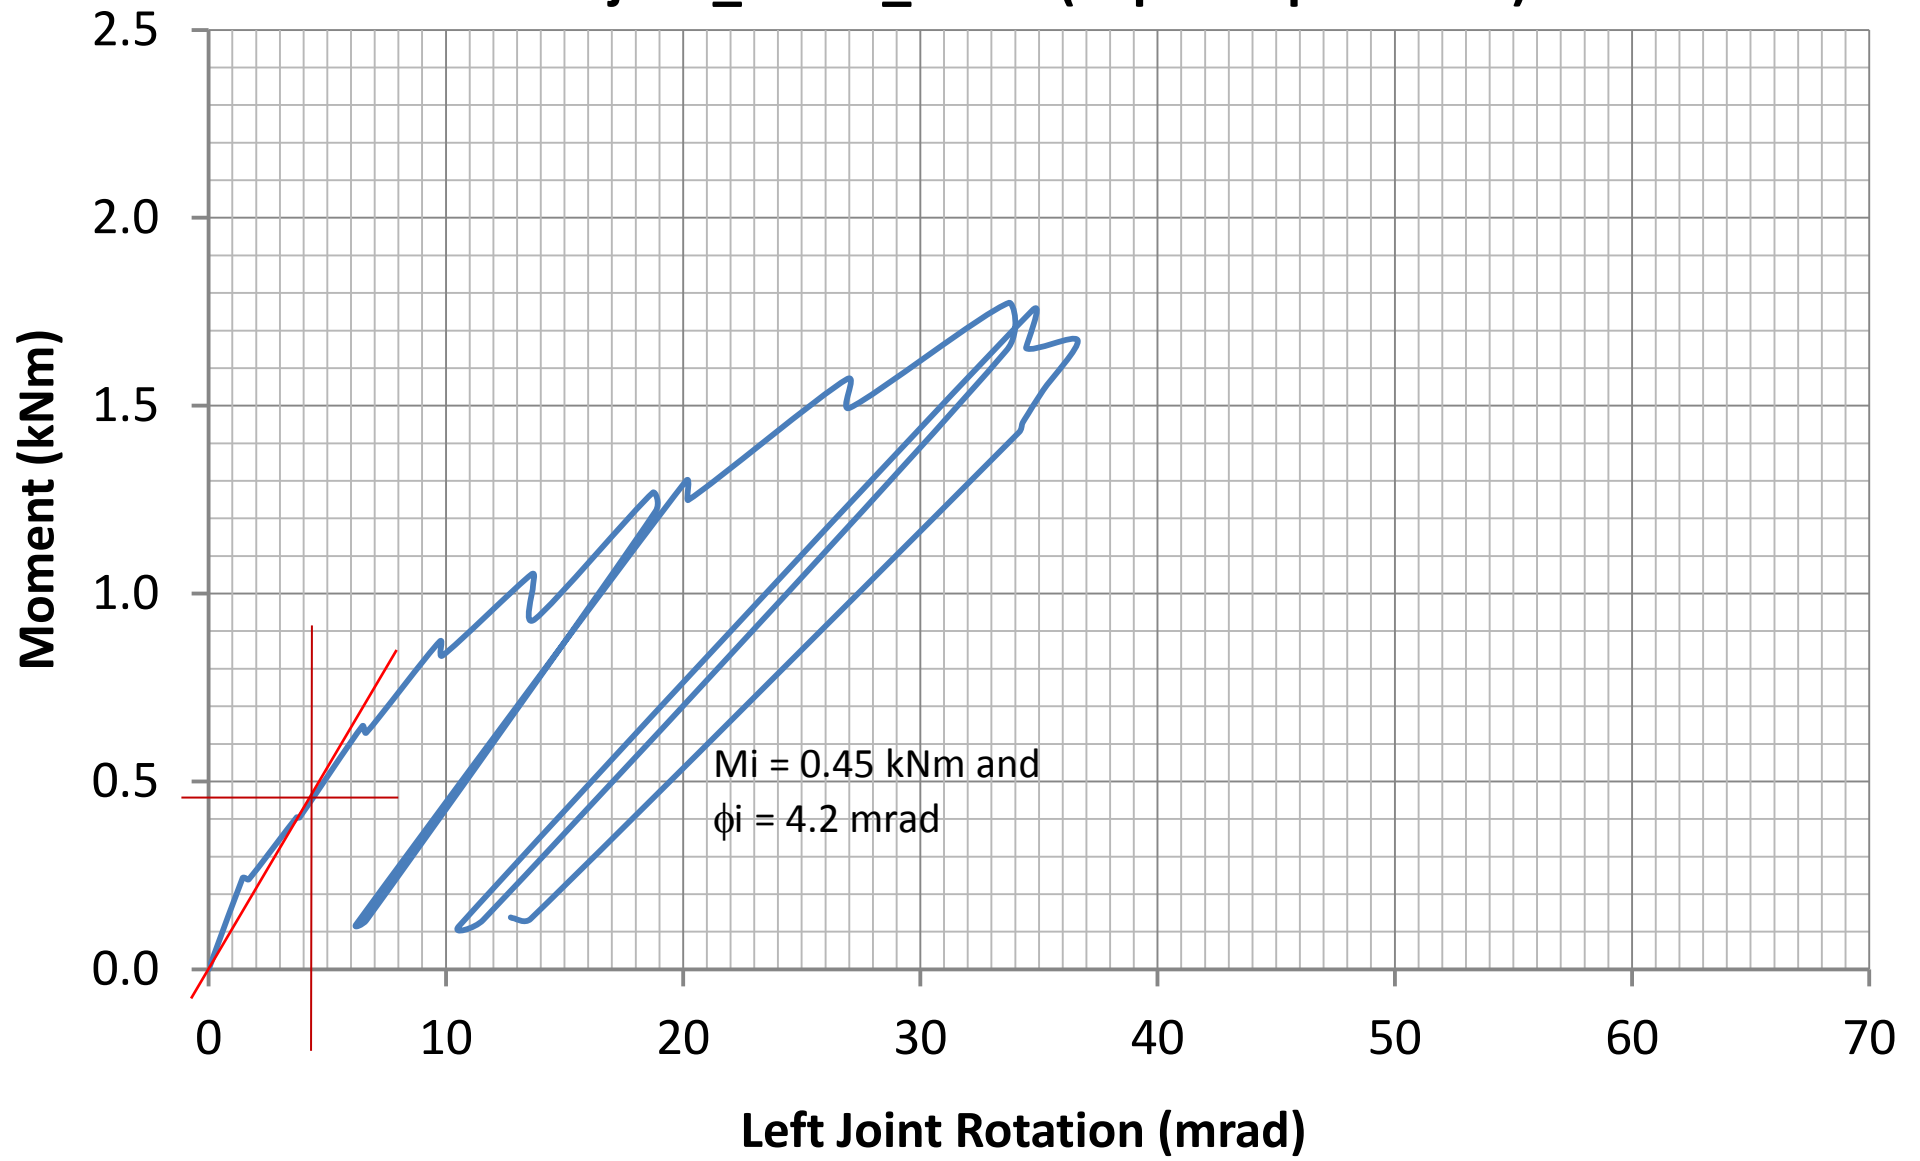

Wmj254_3M16_FC1.5 (Slip Compensated)

